RESEARCHERID THOMSON REUTERS [Aviral et al., 5(11), Nov 2020]

ISSN : 2455-9679 Impact Factor : 3.805



INTERNATIONAL JOURNAL OF RECENT TECHNOLOGY SCIENCE & MANAGEMENT

"OPTIMIZATION OF TURNING PROCESS PARAMETERS FOR CHANGE IN HARDNESS OF EN 8 MATERIAL SPECIMEN USING TAGUCHI METHOD"

Ms. Aviral singh¹, Prof. Ashish Yadav², Prof. Kamlesh kushwaha³

¹ ME (PIS), Department of Mechanical Engineerin, Maharana Pratap College of Technology, Gwalior, Madhya Pradesh, India

²Assistant Professor, Department of Mechanical Engineerin, Maharana Pratap College of Technology, Gwalior, Madhya Pradesh, India

³ Assistant Professor & Head, Department of Mechanical Engineerin, Maharana Pratap College of Technology, Gwalior, Madhya Pradesh, India

ABSTRACT

A conventional method to manufacture parts to a specific dimension involves the removal of excess material by machining operation with the help of cutting tool. Turning process is the one of the methods to remove material from parts. In this work the relation among change in hardness on on the material surface because of the turning operation with respect to different machining parameters like spindle speed, feed and depth of cut have been investigated. Taguchi method has been used to plan the experiments and EN 8 metal selected as a work piece and coated carbide tool as a tool material in this work and hardness after turning has been measured on Brinell harness tester. The obtained experimental data has been analyzed using signal to noise and. The main effects have been measured and percentage contribution of various process parameters affecting hardness also determined.

Key Words: Turing, Taguchi, EN 8 Rockwell Scale, S/N ratio, Regression.

I. INTRODUCTION

Globalization of world market creates a challenge in products marketing, due to high competition induces in manufacturing to produce better quality product within a shorter period of time as well as low cost. Precise product could be produced while utilizing the machine as optimum working condition. Optimum machining parameters are of great concern in the manufacturing environment, where the economy of machining operation plays a key role in competitiveness in the market.

1.1 Lathe machine

A lathe machine is a machine tool that is used to extract metals from a work piece to give the desired shape and size. In other words, it is a machine that

is used to hold a work piece to remove various pieces, such as with the help of turning, grooving, chamfering, knurling, facing, tools.

1.2 Turning operation

A common method to create specific dimension involves the removal of excess material by machining operation by cutting tool. Turning process is the process of remove material from cylindrical and non-cylindrical parts. It is used to

http://www.ijrtsm.com@ International Journal of Recent Technology Science & Management

THOMSON REUTERS

[Aviral et al., 5(11), Nov 2020]

reduce the diameter of the work piece, usually to a specified or different diameter.

1.3 Brinell hardness

The Brinell hardness was the first widely used and standardized hardness test in engineering and metallurgy proposed in 1900 by Swedish engineer Johann August Brinl. The large size of indentation and the potential disadvantage for testing - the piece limits its usefulness. However, its useful feature was also that the hardness VU divided by two gave the estimated UTS in KSI for steels. This characteristic sometimes contributed to hardness testing in its early lap.

$BHN = \frac{applied \ load \ in \ kg}{area \ of \ impression \ or}$ indention in mm

II. TAGUCHI METHOD

Taguchi method is a powerful tool for the design of high quality systems. It provides simple, efficient and systematic approach to optimize design for performance, quality and cost. Taguchi method is efficient method for designing process that operates consistently and optimally over a variety of conditions. Taguchi approach to design the of experiments easy to adopt and apply for users with limited knowledge of statics, hence gained wide popularity in the engineering and scientific community. The desired cutting parameters determined by handbook.



Figure 2.1 Procedure & Steps of Taguchi Perameter Design

III. EXPERIMENTAL SATUP

3.1 Work piece material

The work piece material selected for investigation is EN 8 steel. En 8 finds wide varieties of application not only for forging, casting, axel shaft, crank shaft and connecting rods but also used for low cost die material in tool and die making industries. This steel can be hardened and tempered to provide a greater strength and wear resistance in comparison in low carbon steels. The work piece

used for experiment is round bar with 40 mm diameter and 165 mm length.

used for experiment is round bar with 40 mm diameter and 165 mm length.

THOMSON REUTERS

[Aviral et al., 5(11), Nov 2020]

Specification of work material

Chemical composition

Elements

С	=	0.35 - 0.45%
Mn	=	0.60 - 1.00%
Si	=	0.05 - 0.35%
S	=	0.06% max
Р	=	0.6% max

Machining Process

The cutting tests were performed on medium duty conventional lathe machine and coated carbide tool. The experiments were conducted as per the orthogonal array and hardness for various combinations of parameters was measured using Brinell hardness tester.

Plan of Experiment

The experiment was planned using Taguchi's orthogonal array in the design of experiments, which help in reducing the number of experiments. The L9 orthogonal array. The cutting parameter identified were spindle speed, feed rate and depth of cut. The controls parameter and their level indicated in table.

		Levels		
S.No.	Process Parameter	Low	Medium	High
1.	Spindle speed (rpm)	650	950	1250
2.	Feed Rate (mm/rev)	0.2	0.3	0.4
3.	Depth of Cut (mm)	1	1.5	2

Table 3.1Process and parameters and their level

http://www.ijrtsm.com© International Journal of Recent Technology Science & Management

RESEARCHERID THOMSON REUTERS [Aviral et al., 5(11), Nov 2020]

Table 3.2 The Basic Taguchi L₉ orthogonal array

Experiment	P1	P2	P3
1	1	1	1
2	1	2	2
3	1	3	3
4	2	1	2
5	2	2	3
6	2	3	1
7	3	1	3
8	3	2	1
9	3	3	2

Table 3.3 Consolidated design of experiment table

EN.	(Ss)	(F)	(D)	Hardness (BHN)
1	650	0.2	1	213.46
2	650	0.3	1.5	221.96
3	650	0.4	2	200.12
4	950	0.2	1.5	209.98
5	950	0.3	2	211.32
6	950	0.4	1	234.48
7	1250	0.2	2	212.25
8	1250	0.3	1	207.65
9	1250	0.4	1.5	209.05

IV. ANALYSIS OF THE SIGNAL TO NOISE (S/N) RATIO

Higher the better

It is when the occurrences of some undesirable product characteristics is to be maximized. It is given by $S/N=-10 \ X \ log10(\Sigma(1/yi^2)/N)$

Hardness for each of the parameter at each level is calculated. These also called as main effects.

http://www.ijrtsm.com@International Journal of Recent Technology Science & Management



Table 4.1	S/N Ratio	Summary	Sheet
-----------	-----------	---------	-------

Exp. No	Hardness (BHN)	S/N ratio (dB)
1	213.46	46.58
2	221.96	46.92
3	200.12	46.02
4	209.98	46.44
5	211.32	46.49
6	234.48	47.40
7	212.25	46.53
8	207.65	46.34
9	209.05	46.40

Table 4.2 Mean response table for hardness

Symbol	Controllable	Hardness (BHN)		
Symbol	Factors	L	М	Н
Ss	Spindle speed (rpm)	213.84	218.59	209.65
F	Feed Rate (mm/rev)	211.89	213.64	214.55
D	Depth of Cut (mm)	218.53	213.66	207.89

Table4.3 Mean response of S/N for hardness

Symbol	Controllable Factors		ratio v ess (dB) M	alue of H
Ss	Spindle speed (rpm)	46.50	46.77	46.42
F	Feed Rate (mm/rev)	46.51	46.58	46.60
D	Depth of Cut (mm)	46.77	46.58	46.34

the level that gives the highest value of parameter in each level in the experimental region denoted by bold letter. The estimated main effects can be used for this purpose.

http://www.ijrtsm.com@International Journal of Recent Technology Science & Management



V. MAIN EFFECTS

Main effects plots for the experiments have been given below.

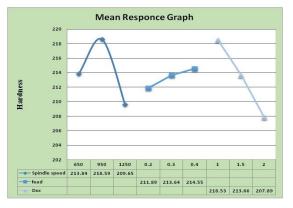


Figure 5.1 Mean response graph for three turning paremeter

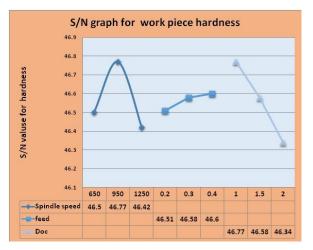


Figure 5.2 Mean S/N graph for hardness

Table 5.3 final comparison of confirmation of experiment for hardness

Results	Actual Experiment al Value	Prediction (Taguchi Method)	Prediction (Regression Modelling)
Level Hardne	S2 + F3+ D1	S2 + F3+ D1 224.95	S2 + F3+ D1 219.65
SS (BHN) S/N Ratio	47.40	47.04	46.83
(dB)			

http://www.ijrtsm.com@International Journal of Recent Technology Science & Management

THOMSON REUTERS

[Aviral et al., 5(11), Nov 2020]

From the response graph plotted between turning parameters and hardness of EN 8, it is observed that there is increase in hardness as the speed is increased at 950 rpm but when speed is further increased hardness goes decreased. The hardness increases when feed rate is changed from 0.2 mm/rev to 0.3 mm/rev and 0.3 to 0.4 mm/rev, but when depth of cut is 1 mm then hardness increases, but as the depth of cut is further increased then hardness decrease considerably.

5.1 Conformation of experiment

While considering three factors the experiments were conducted and result is that the combination of Higher Spindle speed (Ss3), higher Feed rate ((F3) and lower Depth of cut (D1), then the Hardness is maximum.

Table 5.4 final confirmation of experiment

Hardness (BHN)	S/N ratio (dB)
234.48	47.40

VI. MATHEMATICAL REGRESSION MODELLING

For the combination of parameters setting hardness value for EN 8 is tabulated. Empirical formula has fined out by using regression modeling. Modeling of parameters To generalize the results, the Modeling of input parameters (Spindle Speed, Feed rate, Depth of cut) and output parameter (Hardness) is done using REGRESSION MODELLING and MATLAB Software R2011b.

H = 236.37 (Spindle speed) ^{-0.0087}* (Feed rate) ^{0.0150}* (Depth of cut) ^{-0.0694}-1

Comparison of Result

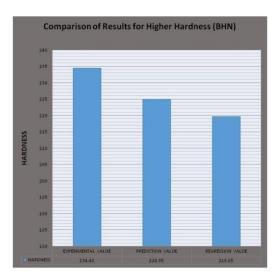


Figure 6.1 Comparison of result for higher hardness

6.1 Summary

In the present work, the relationship between hardness and various process parameters namely spindle speed, feed rate and depth of cut has been developed. Taguchi method has been adopted for the design of experiments and the results have been analyzed by maximize S/N ratio.

http://www.ijrtsm.com@International Journal of Recent Technology Science & Management

RESEARCHERID THOMSON REUTERS [Aviral et al., 5(11), Nov 2020]

VII. ACKNOWLEDGEMENT

We gratefully acknowledge the inspiration provided by Dr. Sanjay Gomasta (Director) Professor Ashish yadav (Guide), Professor kamlesh kushwaha (HOD) and Professor Sanjay goyal of M.P.C.T. Gwalior to complete this research. At last but not least we are very thankful to God who has blessed us to accomplish this work.

REFERENCES

- [1] AL. Arumugam R. Ragothsingh (2013) "Optimization of Turning Process Parameters for Hardness in Forged Steel" International Journal of Engineering Research & Technology (IJERT) Vol. 2 Issue 12, PP- 2401-2405.
- [2] Digvijay kushwah and Ravi Ranjan (2017) " Evaluation and optimization of cutting for parameters turning of EN 8 steel. A Taguchi Appproach." International Journal of Mechanical Engineering (IJME) Vol. 6, Issue 4, PP- 35-44
- [3] Satish Kumar and Ravi Bishnoi (2019) "Optimization of Turning Process Parameters using Taguchi Method" International Journal For Technological Research In Engineering Volume 6, Issue 11, PP 5800-5803.
- [4] Ankit Dogra, Hartaj Singh, Dharampal, Vishal Singh and Sunil Kumar (2016) "Optimization of Turning Parameters of En-8 Steel Cylindrical Rods Using Taguchi Methodology" International Journal for Research in Applied Science & Engineering Technology (IJRASET). Volume 4 Issues XII, PP- 97-103.
- [5] S.Sathiyaraj, A.Elanthiraiyan, G.Haripriya and V.Srikanth Pari (2015) "Optimization of machining parameters for EN 8 steel using Taguchi Method" ICRAMET, Special Issue 9, ISSN: 0974-2115, PP-157-161.
- [6] P. G. Inamdar, N. S. Bagal, V. P. Patil, K. K. Bhosale and V. V. Mane (2017) "Optimization of Surface Roughness in Turning Operation of EN8 using Taguchi Method" International Advanced Research Journal in Science, Engineering and Technology, Vol. 4, Special Issue 1, PP-127-132.
- [7] B.Suresh, Pon.Azhagiri, T.Senthil Kumar and B.Kumarakurubaran (2016) "Experimental Investigation on Surface Roughness and Material Removal Rate during Turning of EN8 Steel" International Journal of Emerging Technologies in Engineering Research (IJETER) Volume 4, Issue 6, PP-142-154.
- [8] G. Akhtar, CheHaron C.H., Ghani J.A. (2008) "Application of Taguchi methodology in optimization of turning parameters for surface roughness". International Journal of Science Engineering and Technology Vol. 1, No. 3, PP-60-66.
- [9] Sijo MT and Biju N, 2010, "Taguchi method for optimization of cutting parameters in turning operations" AMAE.2010.01.536 PP-103-105.
- [10] ChowdharyDr. SS, Khedkar SS, Borkar N.B. "Optimization of process parameters using Taguchi approach with minimum volume lubrication for turning". International Journal of Engineering Research and Applications (IJERA) ISSN: 2248–9622, Vol. 1, Issue 4, pp.1268–1273.

The books

- [11] BelavendramNicolo, (2001), "Design by Quality- Taguchi Techniques for Industrial Use, Prentice Hall, Great Britain".
- [12] Philip J. Ross, (2005), "Teguchi Techniques for Quality Engineering" Tata Mac Gray Hill 2nd edition.

THOMSON REUTERS

[Aviral et al., 5(11), Nov 2020]

Web resource

http://nptel.iitm.ac.in/courses/Webcourse_contents/IIT%20Kharagpur/Manuf%20Proc%20II/New_index1.html

http://www.ee.iitb.ac.in/~apte/CV_PRA_TAGUCHI_INTRO.htm

http://www.camo.com/rt/Resources/design of experiment.html

 $\underline{citeseerx.ist.psu.edu/viewdoc/download?doi{=}10.1.1.80...rep$

http://www.woodcousa.com/Hardness-defs.htm#Rockwell%20C%20Hardness

 $\underline{https://controls.engin.umich.edu/wiki/index.php/Design_of_experiments_via_taguchi_methods:_orthogonal_arrays$